

Product information

REV20188

TEADIT TF 1510

Description:

TEADIT TF 1510 is a highly compressible PTFE - Gasket - Sheet manufactured by a unique process which provides a high level of fibrillation to overcome the creep relaxation and cold flow problems associated with standard (skived or moulded) PTFE sheets. TEADIT TF 1510 is produced from virgin PTFE resin filled with hollow glass micro spheres.

Advantages:

- TEADIT TF 1510 is suitable for service with a wide variety of aggressive fluids, including hydrocarbons, acids and caustics, solvents, water, steam, hydrogen-peroxide, refrigerants, etc.
- Excellent mechanical strength and high stress retention value.
- The high compressibility of TEADIT TF 1510 makes it particularly suitable for use with stress sensitive and/or fragile flanged joints, e.g. glass, ceramics, plastic, etc.
- The excellent malleability of TEADIT TF 1510 makes repairing of small damages and/or irregularities of the sealing area (flange surface) unnecessary.
- TEADIT TF 1510 is quick and simple to install. The used gasket can be removed easily and without residue.

Properties:



- Color: white
- Size: Sheets of 1500 mm x 1500 mm
- Thickness: 1.5 mm up to 3.0 mm
- Temperature: -268 °C to +260 °C
- Chemical resistance: chemically inert against all substances (pH 0-14), including the most aggressive acids and lyes. It is not recommended for strong caustic service above 80°C. It may not be used in contact with molten alkali metals and elemental fluorine at high temperature and high pressure.
- Operating Pressure: 55 bar
- Aging: TEADIT **TF 1510** is not subject to aging or weathering. It can be stored indefinitely.
- FLAME RESISTANT!
- Can be used with oxygen

Approvals:

- TA Luft
- Blow-out

Tests:

- BAM

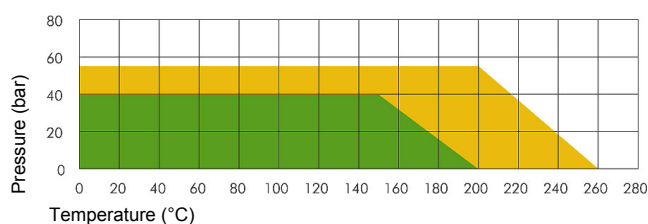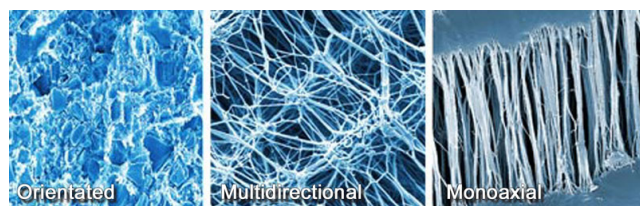

P x T diagram:

The P x T diagram above indicates the service limits considering the simultaneous influence of pressure and temperature. The green area represents the normal service limits, while the orange colored area shows the maximum application limits.

Los parámetros de aplicación indicados en este folleto son típicos. Para cada aplicación específica deberá ser realizado un estudio independiente y una evaluación de compatibilidad. Consultenos con relación a recomendaciones para aplicaciones específicas. Un error en la selección del producto más adecuado o en su aplicación puede resultar en daños materiales y/o en serios riesgos personales, siendo que Teadit no se responsabiliza por el uso inadecuado de las informaciones constantes en el presente folleto, ni por imprudencia, negligencia o impericia en su utilización, colocando sus técnicos a disposición de los consumidores para aclarar dudas y dar orientaciones adecuadas en relación a aplicaciones específicas. Estas especificaciones están sujetas a cambios sin previo aviso, siendo que esta edición substituye todas las anteriores

TEADIT TF 1510		
Technical Parameters	Unit	TEADIT TF 1510
Thickness	[mm]	1,5 / 2,0 / 3,0
Sheet dimensions	[mm]	1500 x 1500
Filler		Glass micro spheres
Color material		white
Color printing		blue
Operating Temperature Range	[°C]	- 268 to + 260
Operating pressure	[bar]	Vacuum to 83
Gasket factors acc. DIN28090-2		
Compression (room temperature) ϵ_{KSW}	[%]	>30
Creep relaxation (room temperature) ϵ_{KRW}	[%]	>4
Compression (elevated temperature) ϵ_{WSW}	[%]	<40
Gasket factors acc. ASTM		
Compressibility ASTM F 36M (34,5 MPa)	[%]	50
Recovery ASTM F 36M (34,5 MPa)	[%]	16
Creep ASTM F 38 (100 °C)	[%]	40
Other Properties		
Residual stress DIN 52913	MPa	13
Leakage rate TA Luft / VDI 2240	mbar*I/(s*m)	1,1*10-5
Leakage rate DIN 3535-6 (40bar, N2)	ml/min	<0,01
Tensile strength ASTM F 152	MPa	14
Gasket factor "m" ASTM		2 (for 2,0 mm)
Minimum gasket stress "y Stress" ASTM	psi	2300 (for 2,0 mm)

Los parámetros de aplicación indicados en este folleto son típicos. Para cada aplicación específica deberá ser realizado un estudio independiente y una evaluación de compatibilidad. Consulten con relación a recomendaciones para aplicaciones específicas. Un error en la selección del producto más adecuado o en su aplicación puede resultar en daños materiales y/o en serios riesgos personales, siendo que Teadit no se responsabiliza por el uso inadecuado de las informaciones constantes en el presente folleto, ni por imprudencia, negligencia o impericia en su utilización, colocando sus técnicos a disposición de los consumidores para aclarar dudas y dar orientaciones adecuadas en relación a aplicaciones específicas. Estas especificaciones están sujetas a cambios sin previo aviso, siendo que esta edición sustituye todas las anteriores